

---

# Efficiency of Medical Workers' Uniforms with Antimicrobial Activity

---

Urška Rozman, Daniela Zavec Pavlinić, Emil Pal,  
Vida Gönc and Sonja Šostar Turk

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/intechopen.68830>

---

## Abstract

Antimicrobial finishing of textiles protects users from pathogenic microorganisms, which can cause medical and hygienic problem. The use of such textiles particularly increases in healthcare facilities, where reduction and transmission of pathogenic bacteria are important factors for preventing nosocomial infections. In the present study, the efficiency of fabric with silane quaternary ammonium compounds (Si-QAC) applied as active agents was evaluated. A test was performed according to ATCC 100-1999 Test Method after 0-, 24- and 48-hour incubation times. The treated textiles were effective against *Enterococcus faecalis*, *Staphylococcus aureus* and *Klebsiella pneumoniae*, but were not effective for Gram-negative *Escherichia coli* and *Pseudomonas aeruginosa*. Testing was also performed in hospital environment at infectious department where working clothes made of treated fabric were compared to normal working clothes. Antimicrobial textiles were not effective in a hospital environment, where average microbial count on medical workers' uniforms without antimicrobial protection was  $1.4 \times 10^9$  cfu/mL, and  $1.3 \times 10^9$  cfu/mL for uniforms made of antimicrobial material. Our conclusion is that quantities of application rates for Si-QAC should be higher or should be improved with applying another antimicrobial coating to obtain complex with dual activity.

**Keywords:** antimicrobial textiles, silane quaternary ammonium compounds, antimicrobial finished textiles test methods, medical workers' uniforms, healthcare-associated infections

---


## 1. Introduction

Hospital textiles, together with moisture and heat, create the right conditions for growth, proliferation and long-term survival of many microorganisms, which can serve as a vector of cross-transmission of healthcare-associated infections (HCAI) [1, 2]. Medical workers'

uniforms can easily become contaminated and there are several reports of uniforms contamination by pathogenic microorganisms [3–5]. HCAI do not only represent complications in the treatment of patients [6, 7], but also cause economic damage with annual financial losses in Europe estimated at 7 billion EUR. Therefore, the medical institutions are increasingly using fabrics with antimicrobial activity, for reducing the transmission of HCAI. Various antimicrobial textile materials are developed using a variety of active agents including triclosan, metals and their salts, phenols, quaternary ammonium compounds (QAC), and organometallics [8]. The aim of our study was to test the efficiency of fabric with silane quaternary ammonium compounds (Si-QAC) applied as active agents in laboratory environment as well as in hospital environment.

## 2. Properties of antimicrobial textiles

The finishing process in textile manufacturing industry gives special, enhanced antimicrobial characteristics to the fabric, that can be biocidal (i.e. include agents that kill microorganisms) or biostatic (i.e. inhibit the microorganisms' growth). Various antimicrobial textile materials are developed using a variety of active agents which include synthetic antimicrobial agents such as triclosan, metal and their salts, phenols, quaternary ammonium compounds (QAC), and organometallics. When evaluating antimicrobial treated textiles the principle of antimicrobial agent fixation (**Figure 1**) to the fabric is crucial, since it is closely related to the mechanism of antimicrobial activity [9, 10]. Leaching antimicrobials that are not chemically bound to the textile are gradually and persistently released from the textile into their surroundings where they demonstrate their antimicrobial activity. On the other hand, the chemically bound antimicrobials are bound to the surface of the textile fibres and act as a barrier for the microorganisms with which they come into contact (principle of bio-barrier formation) [11, 12]. Some of the most common antimicrobial textile finishes, their principles of functioning with positive and negative features are presented in **Table 1**.

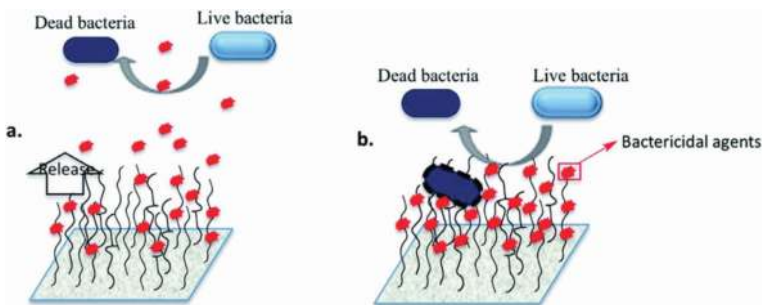

**Figure 1.** Principle of antimicrobial agent fixation and mode of action (a) leaching antimicrobial agent released from the textile, (b) contact killing coating bonded to the textile [11].

Antimicrobial agent	Principle of functioning	Positive/negative features
N-halamines [13, 14]	Electrophilic substitution of Cl in the N-Cl bond with H in the presence of water and results in the transfer of Cl <sup>+</sup> ions that can bind to acceptor regions on microorganisms. This hinders enzymatic and metabolic processes, leading to the destruction of the microorganisms	+ biocides that are active for a broad spectrum of bacteria, fungi and viruses - as an N-H bond, which does not have antimicrobial properties, is formed in the substitution reaction, further exposure of the agent to dilute sodium hypochlorite is needed for regeneration of its antimicrobial activity
Triclosan	By using electro chemical mode of action active substance penetrate and disrupt cell wall, leading to leaking of metabolites and disabling cell functions [15]	+ it is not water solubel and does not leach out [16]
Chitosan [17-19]	Positively charged amino groups can bind to the negatively charged bacterial surface, resulting in the disruption of the cell membrane and an increase in its permeability. Such antimicrobial function is very similar to that determined for QAS. Chitosan can also interact with the DNA of microorganisms to prevent protein synthesis	+ nontoxicity, biocompatibility and biodegradability - weak adhesion to cellulose fibres, resulting in a gradual leaching from the fibre surface with repetitive washing
Metals (Ag, Co, Zn), metal compounds and nanoparticles of metals [20, 21]	Oxidative stress resulting in damage to the lipids, binding and inactivation of intracellular proteins [22], inhibiting active enzyme centres in microorganisms [16] and losses replication ability of microorganisms DNA	+ nano-sized inorganic particles possess high surface area/volume ratio and display unique physical and chemical properties Ag: low toxicity to animals' cell [23]
Bioactive Plant-based Antimicrobial Agents [24, 25]	mostly secondary metabolites such as alkaloids, steroids, tannins, and phenol compounds resembling endogenous metabolites, ligands, hormones, signal transduction molecules or neurotransmitters	+: enable the production of safe, nontoxic, skin and environment friendly bioactive textile products
QAC [26-30]	Interactions between the cationic ammonium group of the QAC and the negatively charged cell membrane of the microbe; these interactions consequently result in the formation of a surfactant-microbe complex. This in turn causes the interruption of all essential functions of the cell membrane: the denaturation of proteins and interruption of protein activity, causing disruption of the cell structure [22]	+: active against a broad spectrum of microorganisms such as Gram-positive and Gram-negative bacteria, fungi and certain types of viruses -: QASs have an inherent weakness: leaching from the textile. To fix a QAS on textile fibres, sol-gel technology has also been used in antimicrobial textiles. This enables the formation of a nanocomposite polymer network with an organic-inorganic hybrid structure (e.g Si-QAC)

**Table 1.** Principles of functioning with positive and negative features of selected antimicrobial textile finishes.

Today, there are different available antimicrobial agents on the market to give textiles antimicrobial characteristics. Each antimicrobial agent has different modes of action and is chosen according to the end use of a textile product [31].

### 2.1. Methods for application of antimicrobial agents

Antimicrobial agent can be applied by different methods. Active agent can be added before the polymer extrusion in the spinning process producing fibres or films. In case of antimicrobial fibres, the antimicrobial agent is integrated into the fibre, while antimicrobial films act as a barrier to microorganisms, but can make fabric impermeable to airflow leading to heat stress [32, 33].

Another procedure to obtain textile with antimicrobial protection is adding the active agent in the phase of textile finishing, where active agent can be applied on fibres or on the flat surfaces. The application can be obtained during processes of exhaustion, pad-dry-curing, coating, spraying and foam technique [16, 32].

### 2.2. Functionalization of textiles by Si-QAC

Quaternary ammonium compounds (QAC) are a chemical class of cationic surface active agents [12]. Once the microorganisms are exposed to the QAC, the agent absorbs and penetrates into the cell wall where it reacts with the cytoplasmic membrane (lipid or protein) leading to membrane disorganization. Low-weight intracellular material is leaking out, which leads to degradation of proteins and nucleic acids and finally autolytic enzymes cause lysis of the cell wall [34, 35]. Although being chemically bonded to the textile fibres and their concentration does not change with time, they cannot ensure the permanent antimicrobial activity of agents because the settling of dead microorganisms on the bio-barrier can greatly reduce or even eliminate their effectiveness [36]. There is proven antimicrobial activity of QAC on natural cellulosic fibres, polyester/cotton blends and secondary acetates [16, 22].

The active ingredient dimethyltetradecyl[3-(trimethoxysilyl)propyl]ammoniumchloride of tested antimicrobial agent consists of a silan group, positively charged ammonium group and long non-polar chain (**Figure 2**). The antimicrobial agent is applied using Foulard process. In the clamping frame, the silan group is bound to the fibre using heat and a condensation reaction, where QAC agent is covalently bound to the fibre (**Figure 3**) [37]. The permanent connection with the neighbouring molecules is formed and the active agent evenly surrounds the fibre.

The SEM imaging of fabric samples (**Figure 3**) shows that covalent bonding of active agent did not cause any noticeable degradation of the fibres and did not affect fibre morphology, indicating that important functional and aesthetic qualities of the fabric were retained. There are no obvious film layers and particles attachments on the treated textiles surfaces.

### 2.3. Durability of antimicrobial treatment using Si-QAC protection

Ideal antimicrobial agents should be effective against a broad spectrum of agents, have low toxicity, be compatible with other finishes, be easy to apply and also be durable and

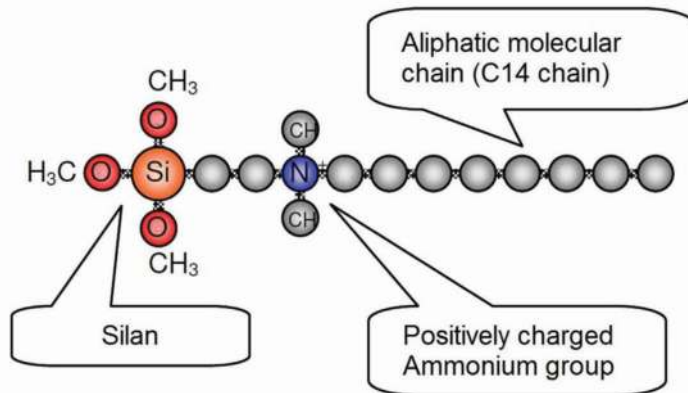


Figure 2. Schematic chemical structure of tested antimicrobial agent.

persistent in washing process. Therefore for many textile applications the wash durability is a key parameter for assessing the performance of antimicrobial treatments [31]. Durability is fundamental to ensuring the antimicrobial performance throughout the life cycle of a textile product. Washing and wear parameters, which can of course lead to a loss of the antimicrobial efficiency, are the key factor for assessing the antimicrobial performance. It is expected that a durable antimicrobial textile finish should survive at least 50 machine washes in line with industrial practices [38]. In our survey Si-QAC treated textiles were washed according to RAL-GZ 992 procedure in 25 and 50 cycles. Antimicrobial protection was decreasing with the number of washing cycles and was totally lost after 50 washing cycles.

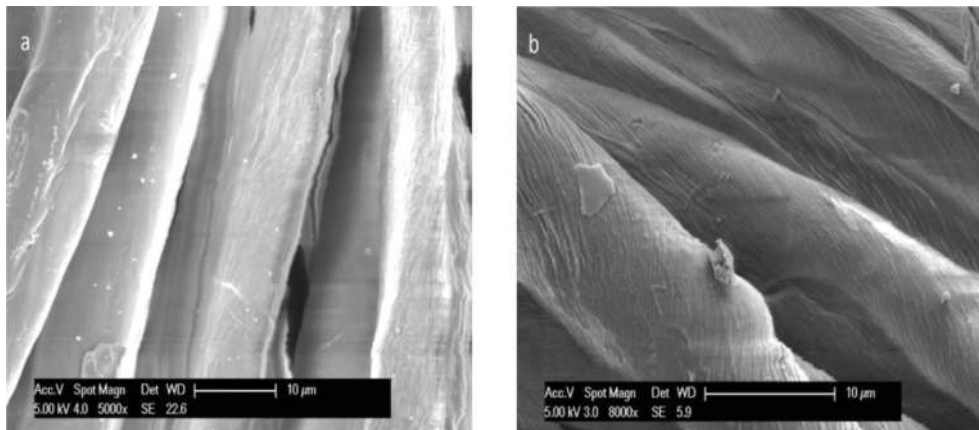


Figure 3. Micromorphology of the textile fibres. (a) SEM image of raw textiles. (b) SEM image of Si-QAC treated textiles. Magnification: 5000 $\times$ .

### 3. Testing and characterization

#### 3.1. Standards and test methods

Proof of activity against bacteria can be performed according to accepted standards and test methods where tested material (e.g. fabric) are compared to standard or an identical material without antimicrobial finishing.

##### 3.1.1. JIS L 1902:2008 (*testing for antibacterial activity and efficacy on textile products*)

This standard specifies the testing method for evaluating the antibacterial activity against bacteria on antibacterial finished textile products. Using one of the following methods:

- Qualitative test (halo method) to evaluate antibacterial activity of textile products by the existence of halos, and applicable to those of which antibacterial finishes chemicals can diffuse into the plate agar culture medium.
- Quantitative test to evaluate antibacterial activity of textile products by bacteriostatic activity value, bactericidal activity value, bacterial decrease value. The absorption method shall be applied for high humidity conditions and printing method for low humidity conditions. Bacteria are shaken out after the incubation of inoculated test pieces.

The measurement of bacterial concentration shall be carried out by viable plate counting or luminescence method for determining ATP (Adenosine Tri-phosphate) concentration [39].

##### 3.1.2. DIN EN ISO 20743

This International Standard specifies quantitative test methods to determine the antibacterial activity of all antibacterial textile products including nonwovens, with different types of used of antibacterial agents or the application methods. The user can select out of three inoculation methods for antibacterial activity determination:

- Absorption method where the test bacterial suspension is inoculated directly onto tested surfaces;
- Transfer method where the test bacteria are placed on an agar plate and transferred onto tested surfaces; and
- Printing method where the test bacteria are placed on a filter and printed onto tested surfaces.

For measuring the enumeration of bacteria colony, the viable plate counting method and the ATP luminescence method are also specified [40].

##### 3.1.3. AATCC 147 (*parallel streak method*)

The objective of the method is detecting bacteriostatic activity on textile materials. The method is useful for obtaining a rough estimate of activity. Increasing degrees of sensitivity is indicated


where growth of the inoculum organism is decreasing from one to the other end of each streak and from one to the next streak. Tested surfaces are placed in intimate contact with the inoculated (with test bacterium) agar surface and incubated. Antibacterial activity of the tested material is indicated in clear area of interrupted growth underneath and along the side of the test material [41].

#### 3.1.4. AATCC Test Method 100-1999 (antibacterial finishes on textile materials: assessment of)

This method provides a quantitative procedure for the evaluation of the antibacterial activity degree. Test and control swatches are inoculated with test organisms and incubated. By shaking in known amounts of neutralizing solution, the bacteria are eluted from the swatches. The number of eluted bacteria is determined and percentage reduction by the treated specimen is calculated [42].

### 3.2. Study in laboratory environment

Textiles pieces (50/50 PES/COT white fabric, 195 g/m<sup>2</sup>) with and without Si-QAC dimethyl-tetradecyl[3-(trimethoxysilyl)propyl]ammoniumchlorid were sterilized, dried, artificially contaminated (**Figure 4**) and tested for antimicrobial activity according to ATCC 100-1999 Test Method after 0, 24 and 48 hour incubation times. Ready-made cultures of *Escherichia coli* (DSM 1562),

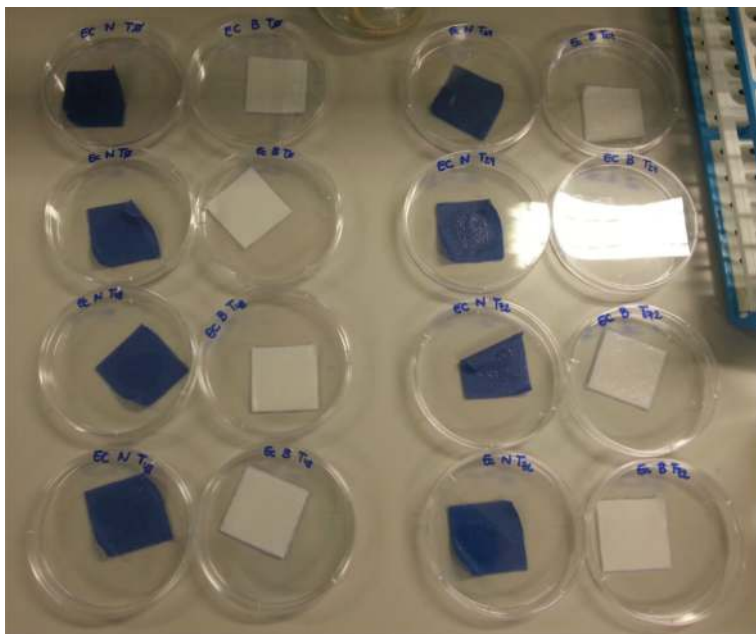


**Figure 4.** Artificially contaminated tested textile pieces with *E. coli* suspension (first and third column textile pieces with Si-QAC, second and fourth column textile pieces without Si-QAC).



*Enterococcus faecalis* (ATCC 29212), *Klebsiella pneumoniae* (ATCC 13883), *Staphylococcus aureus* (ATCC 25923) and *Pseudomonas aeruginosa* (ATCC 27853) were taken from the freezer and grown in nutrient broth (Tryptiyc Soy broth) for 4 days in an incubator at 37°C. Efficiency rate after 24 or 48 hour incubation was calculated using serial dilution, viable plate counting and colony forming units per millilitre (cfu/mL) calculation. Appropriate selective growth medium (e.g. VRBD agar, Kanamycin Esculin Azide agar, *Klebsiella pneumoniae* selective agar, Baird Parker agar, Cetrimide agar) were used.


The performance of fabrics with antimicrobial activity varies and depended on tested microbial species and it is to some extent related to the bacteria Gram categorization (e.g. Gram negative and Gram positive). When comparing textile with antimicrobial activity to nontreated textile the differences in reduction rate were  $3.22 \times 10^2$  cfu/mL for *E. faecalis*,  $1.87 \times 10^4$  cfu/mL for *S. aureus* two representatives of Gram-positive bacteria and  $6.81 \times 10^3$  cfu/mL for Gram-negative *K. pneumoniae* (Figure 5), but treated textiles was not effective for Gram-negative *E. coli* and *P. aeruginosa* (Figure 6).

QACs are membrane active agents with a target site predominantly at the cytoplasmic membrane [43]. Since the cell wall structure varies between G+ and G- bacteria, the differences in sensitivity to QAC are expected. The cell wall of G+ bacteria represents much less effective barrier for the entry of antiseptics and disinfectants, which may explain the sensitivity of these organisms to many antibacterial agents including QACs [44–46]. Gram-negative bacteria are generally more resistant to antiseptics since their outer membrane acts as a barrier that limits

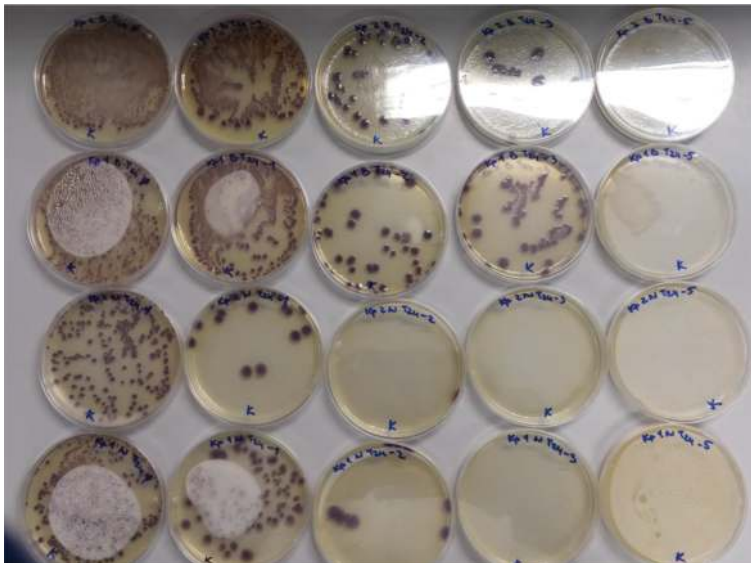

**Figure 5.** Colonies of *K. pneumoniae* after plating serial dilutions of suspension obtained from artificially contaminated textile pieces that were incubated for 24 hours. First and second row: samples without Si-QAC, third and fourth row: samples with Si-QAC.



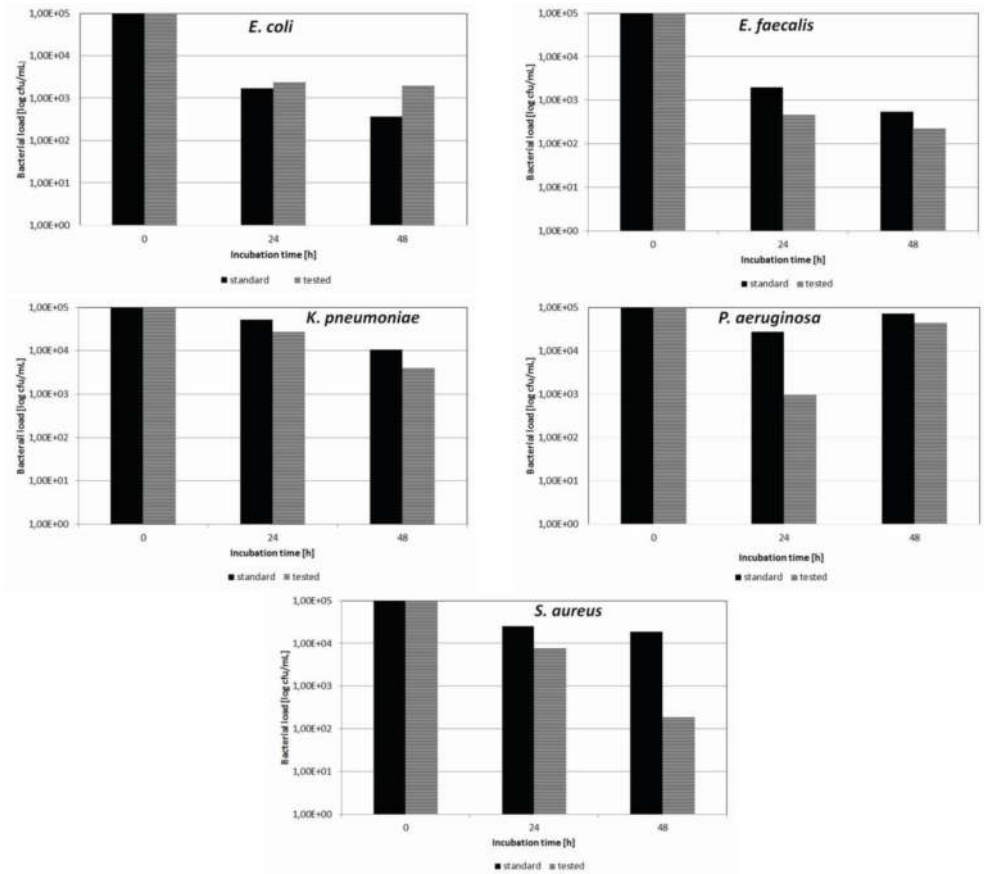

**Figure 6.** Bacteria per mL of eluting solution after 0-, 24- and 48-hour incubation time for  $1 \times 10^5$  cfu/mL inoculum on standard and tested textile pieces.

the entry of many chemically unrelated types of antibacterial agents [47–52]. The formation of biofilm (in case of *P. aeruginosa*) can also account for the reduced sensitivity of bacteria [53].

### 3.3. Study in hospital environment

Medical workers' uniforms were made of antimicrobial material and worn for one day at infectious department by 10 nurses. Normal working clothes were used for negative control. Testing was repeated in two cycles. At the time of testing patient contaminates with MRSA (methicillin-resistant *Staphylococcus aureus*), CRE (carbapenem-resistant Enterobacteriaceae) and bacteria producing ESBL (extended-spectrum beta-lactamases) were hospitalized on the department. After eight-hour shift, uniforms were transferred to laboratory (each uniform in separate sterile bag) and tested for presence of microorganisms. Method of sterile elution was performed as follows: 2 L of sterile elution solution (0.9% NaCl + 0.2% Tween 80) (JIS L 1902,

2008) was added to uniform in a sterile bag and shaken for 30 min at 300 rpm on a shaking machine (Heidolph vibramax 100), after 10, 20 and 30 min uniform was gownned per hand in the closed bag. 100 mL of eluate was sterile filtrated through 0.8  $\mu\text{m}$  0.45  $\mu\text{m}$  membrane filter which was further transferred to 100 mL 0.9% NaCl and shaken vigorously for 1 min. Efficiency rate after 24 or 48 hour incubation was calculated using serial dilution, viable plate counting and colony forming units per millilitre (cfu/mL) calculation. MALDI-TOF analysis of selected morphologically different colonies was used for microorganism identification.

Antimicrobial textiles were not effective in a hospital environment, where average microbial count on medical workers' uniforms without antimicrobial protection was  $1.4 \times 10^9$  cfu/mL, and  $1.3 \times 10^9$  cfu/mL for uniforms made of antimicrobial material. Species of *Acinetobacter lwoffii* (G-), *Bacillus* spp. (G+), *Pseudomonas aeruginosa* (G-), *Pseudomonas alcaliphila*, *Pseudomonas stutzeri*, *Pseudomonas mantelli*, *Pseudomonas putida*, *Staphylococcus epidermidis* (G+), *Staphylococcus lugduensis*, *Staphylococcus warneri* and *Stenotrophomonas maltophilia* (G-) were identified. Our results are consistent with others who had tested uniforms with antimicrobial protection in the real life hospital environment. Burden et al. found no evidence that either antimicrobial scrub product decreased bacterial contamination of HCWs' uniforms or skin after an 8-hour workday [54] or experimental uniforms provided results only slightly in agreement with in vitro data [55]. Despite the fact that the effectiveness of an antimicrobial material was demonstrated in laboratory test, the effectiveness in hospital environment was not present. Bacterial load on medical workers' uniforms was much higher than the concentrations of microorganisms used in laboratory test method, which could also have an effect on the antimicrobial efficiency, since the adsorption of dead microorganisms can affect antimicrobial function of chemical bound agent [12]. Therefore, our conclusion is that quantities of application rates of Si-QAC should be higher. Another approach to improve the effectiveness of antimicrobial protection is the tailoring of different antimicrobial coatings to obtain complex with dual activity (e.g. applying silver chloride and Si-QAC composite) [36, 56–61].

## 4. Application potentials and environmental concerns

By implementing medical workers' uniforms with antimicrobial activity the risk for cross-transmission is reduced, while the fabric itself is protected against potential growth of newly microorganisms. Within the decrease of cross-infections, the protection of users (medical workers, patients, workers in food industry, etc...) is better; moreover, the comfort and well-being at workplace are improved.

### 4.1. Medical workers' uniforms, beddings, and patients' wear

Work clothing of health workers is uniform, has the agreed cut and colour, and is always clean and daily fresh [62]. Its purpose is to protect health workers from direct contact with the patient's secretions and consequently the transfer of microorganisms from patient to medical personnel and later to other patients [63]. The protective and preventing antimicrobial products can be used in different end application and they are ideal to be used in healthcare sectors. Workers' uniforms and bed sheets, which build microenvironment around human body, made of antimicrobial treated fabrics can for example protect humans against nosocomial

infections in the hospital environments. Antimicrobial treatment of textiles aimed for hospital environment is usually marketed with the function of preventing the growth of microorganisms [54]. Antimicrobials for textiles need to fulfil many different criteria including efficacy against microorganisms, suitability for textile processing, durability and a favourable safety and environmental profile [31]. In the field of medical textiles, Ag (silver) and Si-QAC agents are widely used [31].

#### 4.2. Preventing cross-contamination and HCAI

The origin of infection can be an infected person (e.g. patients, health workers or visitors) the environment. Microorganisms can be part of the patient's normal flora that can cause the nosocomial infection during the process of diagnosis, treatment and care of immunocompromised patients. Microorganisms are able to survive on environmental surfaces up to several weeks [64] providing a significant biotransfer/cross-contamination/cross-infection potential [65] that should not be overlooked. Microorganisms can also survive in the patient's abiotic environment, such as contaminated equipment for care, diagnosis and treatment (textiles), food, water, and disinfectants and on surfaces [66], which shows that one of the possible sources of nosocomial pathogens can be inappropriately disinfected textiles [67]. The environment can play a marked role in the nosocomial transmission of microorganisms [68], where garments of healthcare workers are an important aspect of the environment that can easily become contaminated and are therefore recognized as a possible vehicle of nosocomial infections. Hospital textiles could be a source of HCAs, contributing to the transmission of pathogens both through indirect contact, via hospital staff, endogenously, and by means of aerosols [68, 69]. The characteristics of the textile in question, together with humidity and heat, can create the right conditions for the proliferation of numerous microorganisms [2, 3]. Pathogenic bacteria such as MRSA [3], *P. aeruginosa* and *K. pneumoniae* [4] and *C. difficile* [5] were also detected on uniforms of physicians and nurses. Surveys show that hospital textiles can be the source of nosocomial infections with streptococci [70], enterococci [71], *Bacillus cereus* [72], staphylococci [73] and coliform bacteria [74]. In addition, there is continuously increasing trends of antimicrobial resistance among HCAI pathogens leading to raising healthcare costs, prolonged hospital stays, treatment failures, and sometimes death [75].

#### 4.3. Impact on the environment and human health

Although synthetic antimicrobial agents effectively inhibit the growth of microbes, most of them are toxic, can cause adverse effects on human health, and have environmental issues [8]. Recommended application rate of a silane quaternary ammonium compounds are ca. 10,000 mg/kg [76]. Si-QAC consumption in textiles was 1128 tonnes in 2004, most of it being a particular type of Si-QAC [77]. Exposure pathways and potential health effects need to be considered in order to evaluate the safety of antimicrobial compounds for humans. Si-QAC is readily biodegradable (after 6 days, 70% of the substance is degraded) [78] and is also expected to rapidly hydrolyze [79]. The type of active material (free or bound), the concentration in the product, the routes of exposure and the frequency of use all influence the extent to which humans may be exposed to antimicrobials in a textile product [80]. Although Si-QAC is a corrosive chemical, the USEPA does not expect any severe effects of Si-QAC use on human health [79], there is however

evidence of skin sensitization for Si-QAC [78]. For any substance that addresses microorganisms there is a need to consider the potential for development of resistance. Although durable antimicrobials are increasingly popular for the consumer market, questions regarding their use will continue to rise regarding their effect on the evolution of resistant microbes [81]. Due to relatively large quantities of recommended application rates, the bacterial resistance should be considered. Most biocides used on commercial textiles can induce bacterial resistance to these substances, which can lead to increased resistance to certain antibiotics in clinical use [82], but any possible clinical significance of this remains to be tested [22]. Although the number of studies elucidating the association between antimicrobials resistance and resistance to clinical isolates has been limited, recent laboratory studies have confirmed the potential for such a link (e.g. transfer of triclosan resistance) in *E. coli* and *Salmonella enterica*. Thus, widespread use of antimicrobials may represent a potential public health risk in regard to development of concomitant resistance to clinically important antimicrobials [83].

## 5. Conclusion

Working cloths made of textiles with proven antimicrobial protection could be an ideal solution for areas with frequent infections such as healthcare facilities. Ideal antimicrobial agents should be effective against a broad spectrum of agents, have low toxicity, be compatible with other finishes, be easy to apply and be durable and persistent in washing process. Efficiency of antimicrobial textiles could be improved with higher application rates of Si-QAC or additional binding of another antimicrobial agent, but in this connection, the effect on antimicrobial resistance evolution should be considered.

## Author details

Urška Rozman<sup>1\*</sup>, Daniela Zavec Pavlinič<sup>2</sup>, Emil Pal<sup>3</sup>, Vida Gönc<sup>1</sup> and Sonja Šostar Turk<sup>1</sup>

\*Address all correspondence to: [urska.rozman@um.si](mailto:urska.rozman@um.si)

<sup>1</sup> Faculty of Health Sciences, University of Maribor, Maribor, Slovenia

<sup>2</sup> Titera d.o.o., Murska Sobota, Slovenia

<sup>3</sup> General Hospital Murska Sobota, Murska Sobota, Slovenia

## References

- [1] Malnick S, Bardenstein R, Huszar M, Gabbay J, Borkow G. Pyjamas and sheets as a potential source of nosocomial pathogens. *Journal of Hospital Infection* [Internet]. 2008;**70**(1):89-92. Available from: <http://linkinghub.elsevier.com/retrieve/pii/S0195670108002351> [Accessed: November 8, 2016]

- [2] O'Hanlon SJ, Enright MC. A novel bactericidal fabric coating with potent in vitro activity against methicillin-resistant *Staphylococcus aureus* (MRSA). *The International Journal of Antimicrobial Agents* [Internet]. 2009;**33**(5):427-431. Available from: <http://linkinghub.elsevier.com/retrieve/pii/S092485790800527X> [Accessed: November 8, 2016]
- [3] Boyce JM, Potter-Bynoe G, Chenevert C, King T. Environmental contamination due to methicillin-resistant *Staphylococcus aureus*: Possible infection control implications. *Infection Control and Hospital Epidemiology* [Internet]. 1997;**18**(9):622-627. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/9309433> [Accessed: November 8, 2016]
- [4] Wiener-Well Y, Galuty M, Rudensky B, Schlesinger Y, Attias D, Yinnon AM. Nursing and physician attire as possible source of nosocomial infections. *American Journal of Infection Control* [Internet]. 2011;**39**(7):555-559. Available from: <http://linkinghub.elsevier.com/retrieve/pii/S0196655311001179> [Accessed: November 8, 2016]
- [5] Perry C, Marshall R, Jones E. Bacterial contamination of uniforms. *Journal of Hospital Infection* [Internet]. 2001;**48**(3):238-241. Available from: <http://linkinghub.elsevier.com/retrieve/pii/S0195670101909624> [Accessed: November 8, 2016]
- [6] Haley RW, Culver DH, White JW, Morgan WM, Emori TG, Munn VP, et al. The efficacy of infection surveillance and control programs in preventing nosocomial infections in US hospitals. *The American Journal of Epidemiology* [Internet]. 1985;**121**(2):182-205. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/4014115> [Accessed: November 8, 2016]
- [7] Harbarth S, Sax H, Gastmeier P. The preventable proportion of nosocomial infections: An overview of published reports. *Journal of Hospital Infection* [Internet]. 2003;**54**(4):258-266; quiz 321. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/12919755> [Accessed: November 8, 2016]
- [8] Murugesh Babu K, Ravindra KB. Bioactive antimicrobial agents for finishing of textiles for health care products. *Journal of the Textile Institute* [Internet]. 2015;**106**(7):706-717. Available from: <http://www.tandfonline.com/doi/full/10.1080/00405000.2014.936670> [Accessed: November 8, 2016]
- [9] Yuan Gao Y, Cranston R. Recent advances in antimicrobial treatments of textiles. *The Textile Research Journal* [Internet]. 2008;**78**(1):60-72. Available from: <http://journals.sagepub.com/doi/10.1177/0040517507082332> [Accessed: January 31, 2017]
- [10] Abidi N, Kiekens P. Chemical functionalisation of cotton fabric to impart multifunctional properties. *Tekstilec*. 2016;**59**(2):156-161
- [11] Schindler W, Hauser P. Chemical finishing of textiles [Internet]. Woodhead Publishing Limited; 2004 [cited 2017 Jan 27]. 212 p. Available from: <https://books.google.com/books?hl=sl&lr=&id=S42kAgAAQBAJ&oi=fnd&pg=PP1&dq=Chemical+Finishing+of+Textiles&ots=u-U5JjrZ8B&sig=gZTCkhB2NzLLGezYG27b5M3vDpc>
- [12] Simoncic B, Tomsic B. Structures of novel antimicrobial agents for textiles—a review. *The Textile Research Journal* [Internet]. 2010;**80**(16):1721-1737. Available from: <http://journals.sagepub.com/doi/10.1177/0040517510363193> [Accessed: January 27, 2017]

- [13] Barnes K, Liang J, Wu R, Worley SD, Lee J, Broughton RM, et al. Synthesis and antimicrobial applications of 5,5'-ethylenebis[5-methyl-3-(3-triethoxysilylpropyl)hydantoin]. *Biomaterials* [Internet]. 2006;**27**(27):4825-4830. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/16757023> [Accessed: January 27, 2017]
- [14] Liang J, Chen Y, Barnes K, Wu R, Worley SD, Huang T-S. N-halamine/quat siloxane copolymers for use in biocidal coatings. *Biomaterials*. 2006;**27**(11):2495-2501
- [15] Levy CW, Roujeinikova A, Sedelnikova S, Baker PJ, Stuitje AR, Slabas AR, et al. Molecular basis of triclosan activity. *Nature* [Internet]. 1999;**398**(6726):383-384. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/10201369> [Accessed: March 17, 2017]
- [16] Bischof Vukušić S, Gaan S. Antimicrobial protective textiles. In: Bischof Vukušić S, Vujanović E, editors. *Functional protective textiles* [Internet]. Zagreb: University of Zagreb, Faculty of Textile Technology; 2012 [cited 2017 Mar 17]. p. 101-44. Available from: <http://www.worldcat.org/title/functional-protective-textiles/oclc/814043279>
- [17] Oktem T. Surface treatment of cotton fabrics with chitosan. *Coloration Technology* [Internet]. 2003;**119**(4):241-246. Available from: <http://doi.wiley.com/10.1111/j.1478-4408.2003.tb00179.x> [Accessed: January 27, 2017]
- [18] Huang K-S, Wu W-J, Chen J-B, Lian H-S. Application of low-molecular-weight chitosan in durable press finishing. *Carbohydrate Polymers*. 2008;**73**(2):254-260
- [19] Lim S-H, Hudson SM. Synthesis and antimicrobial activity of a water-soluble chitosan derivative with a fiber-reactive group. *Carbohydrate Research*. 2004;**339**(2):313-319
- [20] Kohen R, Nyska A. Oxidation of biological systems: Oxidative stress phenomena, antioxidants, redox reactions, and methods for their quantification. *Toxicologic Pathology* [Internet]. 2002;**30**(6):620-650. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/12512863> [Accessed: January 27, 2017]
- [21] Shahidi S, Wiener J. Antibacterial Agents in Textile Industry. In: Varaprasad B, editor. *Antimicrobial Agents* [Internet]. Rijeka: InTech; 2012 [cited 2017 Feb 1]. p. 337-406. Available from: <http://www.intechopen.com/books/antimicrobial-agents/antibacterial-agents-in-textile-industry>
- [22] McDonnell G, Russell AD. Antiseptics and disinfectants: Activity, action, and resistance. *Clinical Microbiology Reviews* [Internet]. 1999;**12**(1):147-179. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/9880479> [Accessed: January 27, 2017]
- [23] Raffi M, Hussain F, Bhatti TM, Akhter JI, Hameed A, Hasan MM. Antibacterial characterization of silver nanoparticles against *E. coli* ATCC-15224. *Journal of Materials Science and Technology* [Internet]. 2008;**24**(2):192-196. Available from: <http://www.omnis-mg.hr/Radovi/EC-16nm-pakistan.pdf> [Accessed: March 17, 2017]
- [24] Cowan MM. Plant products as antimicrobial agents. *Clinical Microbiology Reviews* [Internet]. 1999;**12**(4):564-582. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/10515903> [Accessed: February 1, 2017]

- [25] Ciocan D, Ioan B. Plant products as antimicrobial agents. Ann "Alexandru Ioan Cuza" University SecII a [Internet]. 2007 [cited 2017 Feb 1];8(1):151-6. Available from: <http://www.gbm.bio.uaic.ro/index.php/gbm/article/view/402>
- [26] Ascenzi JM. Handbook of disinfectants and antiseptics. New York: Marcel Dekker, Inc.; 1996. 161 p.
- [27] Gilbert P, Moore LE. Cationic antiseptics: Diversity of action under a common epithet. Journal of Applied Microbiology [Internet]. 2005;99(4):703-715. Available from: <http://doi.wiley.com/10.1111/j.1365-2672.2005.02664.x> [Accessed: February 1, 2017]
- [28] Ahlström B, Chelminska-Bertilsson M, Thompson RA, Edebo L. Long-chain alkanoylcholines, a new category of soft antimicrobial agents that are enzymatically degradable. Antimicrobial Agents and Chemotherapy [Internet]. 1995;39(1):50-55. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/7695328> [Accessed: February 1, 2017]
- [29] Judeinstein P, Sanchez C, Schubert U, Hüsing N, Lorenz A, Sanchez C, et al. Hybrid organic-inorganic materials: A land of multidisciplinary. Journal of Materials Chemistry [Internet]. 1996;6(4):511-525. Available from: <http://xlink.rsc.org/?DOI=JM9960600511> [Accessed: February 1, 2017]
- [30] Nalwa HS. Handbook of organic-inorganic hybrid materials and nanocomposites. California: American Scientific Publishers; 2003. 810 p.
- [31] Windler L, Height M, Nowack B. Comparative evaluation of antimicrobials for textile applications. Environment International. 2013;53:62-73
- [32] Mao J. Durable antimicrobial finish for cotton with new technology. AATCC Review. 2002;2(12):15-7
- [33] Belkin NL. Effect of laundering on the barrier properties of reusable surgical gown fabrics. American Journal of Infection Control [Internet]. 1999;27(3):304-305; author reply 307-308. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/10358238> [Accessed: March 17, 2017]
- [34] Salton MR. Lytic agents, cell permeability, and monolayer penetrability. The Journal of General Physiology [Internet]. 1968;52(1):227-252. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/19873623> [Accessed: January 31, 2017]
- [35] Denyer SP. Mechanisms of action of antibacterial biocides. International Biodeterioration and Biodegradation. 1995;36:227-245
- [36] Logar N, Danijela K, Tomšič B, Pavko Čuden A, Simončič B. Tailoring of a dual-active antibacterial coating for polylactic acid fibres. Tekstilec. 2016;59(4):289-297
- [37] Achwal WB. Antimicrobial finishes and their modifications. Colourage. 2003;1:58-59
- [38] Sun G, Worley S. Chemistry of durable and regenerable biocidal textiles. The Journal of Chemical Education. 2005;82(1):60-64



- [39] Japanese Industrial Standard. JIS L 1902:2008 testing for antibacterial activity and efficacy on textile products. Japanese Standards Association; 2008. 35 p.
- [40] ISO/TC 38 T. ISO 20743:2013(en), Textiles–determination of antibacterial activity of textile products [Internet]. 2013. Available from: <https://www.iso.org/obp/ui/#iso:std:59586:en> [Accessed: December 19, 2016]
- [41] AATCC Test Method 147-2004. Antibacterial Activity of Textile materials: Parallel streak method. AATCC Technical Manual. Research Triangle Park, NC USA; 2012. pp. 257-8.
- [42] AATCC Test Method 100-1999. Antibacterial Finishes on Textile Materials: Assessment of, AATCC Technical Manual. Research Triangle Park, NC USA; 2004. pp. 149-51.
- [43] Hugo WB. Disinfection mechanisms. In: Russel AD, Hugo WB, Ayliffe GAJ, editors. Principles and practice of disinfection, preservation and sterilization. 3rd ed. Oxford, England: Blackwell Science, Oxford, England; 1999. p. 258-83.
- [44] Russel AD. Modification of the bacterial cell envelope and enhancement of antibiotic susceptibility. In: Stuart-Harris CH, Harris DM, editors. The Control of Antibiotic-Resistant Bacteria. London, England: Academic Press, Ltd.; 1981. pp. 119-165
- [45] Russell AD. Mechanisms of bacterial resistance to biocides. *International Biodeterioration and Biodegradation*. 1995;36:247-265
- [46] Russell AD, Chopra I. Understanding antibacterial action and resistance. Hemel Hempstead UK: E. Horwood; 1990. 246 p.
- [47] Hammond SM, Lambert PA, Rycroft AN. The Bacterial Cell Surface [Internet]. Dordrecht: Springer Netherlands; 1984. Available from: <http://link.springer.com/10.1007/978-94-011-6553-2> [accessed: January 31, 2017]
- [48] Hancock REW. Alterations in outer membrane permeability. *Annual Review of Microbiology* [Internet]. 1984;38(1):237-264. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/6093683> [accessed: January 31, 2017]
- [49] Nikaido H. Prevention of drug access to bacterial targets: permeability barriers and active efflux. *Science* (80-). 1994;264(5157):382-8.
- [50] Paulsen IT, Park JH, Choi PS, Saier MH. A family of gram-negative bacterial outer membrane factors that function in the export of proteins, carbohydrates, drugs and heavy metals from gram-negative bacteria. *FEMS Microbiology Letters* [Internet]. 1997;156(1):1-8. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/9368353> [accessed: January 31, 2017]
- [51] Russell AD, Gould GW. Resistance of enterobacteriaceae to preservatives and disinfectants. *The Journal of Applied Bacteriology* [Internet]. 1988;65(s17):167S-195S. Available from: <http://doi.wiley.com/10.1111/j.1365-2672.1988.tb04651.x> [accessed: January 31, 2017]
- [52] Vaara M. Agents that increase the permeability of the outer membrane. *Microbiology Reviews* [Internet]. 1992;56(3):395-411. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/1406489> [accessed: January 31, 2017]

- [53] Brown MRW, Gilbert P. Sensitivity of biofilms to antimicrobial agents. *The Journal of Applied Bacteriology* [Internet]. 1993;74(S22):87S–97S. Available from: <http://doi.wiley.com/10.1111/j.1365-2672.1993.tb04345.x> [accessed: January 27, 2017]
- [54] Burden M, Keniston A, Frank MG, Brown CA, Zoucha J, Cervantes L, et al. Bacterial contamination of healthcare workers' uniforms: A randomized controlled trial of antimicrobial scrubs. *Journal of Hospital Medicine* [Internet]. 2013;8(7):380-385. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/23757125> [accessed: February 1, 2017]
- [55] Condò C, Messi P, Anacarso I, Sabia C, Iseppi R, Bondi M, et al. Antimicrobial activity of silver doped fabrics for the production of hospital uniforms. *The New Microbiologica*. 2015;38:551-558
- [56] Zhi Li †, Daeyeon Lee ‡, Xiaoxia Sheng †, Robert E. Cohen,\* A, Michael F. Rubner\* †. Two-Level Antibacterial Coating with Both Release-Killing and Contact-Killing Capabilities. *Langmuir*. American Chemical Society; 2006;22(24):9820-3.
- [57] Dwivedi P, Narvi SS, Tewari RP. Coating made from *Pseudotsuga menziesii* phyto-synthesized silver nanoparticles is efficient against *Staphylococcus aureus* biofilm formation. *Nano Life* [Internet]. 2015;5(4):1540006. Available from: <http://www.worldscientific.com/doi/abs/10.1142/S1793984415400061> [accessed: January 31, 2017]
- [58] Mohamed RR, Sabaa MW. Synthesis and characterization of antimicrobial crosslinked carboxymethyl chitosan nanoparticles loaded with silver. *International Journal of Biological Macromolecules*. 2014;69:95-99
- [59] Wang X, Du Y, Fan L, Liu H, Hu Y. Chitosan-metal complexes as antimicrobial agent: Synthesis, characterization and structure-activity study. *Polymer Bulletin* [Internet]. 2005;55(1-2):105-113. Available from: <http://link.springer.com/10.1007/s00289-005-0414-1> [accessed: January 31, 2017]
- [60] El-Shafei A, Abou-Okeil A. ZnO/carboxymethyl chitosan bionano-composite to impart antibacterial and UV protection for cotton fabric. *Carbohydrate Polymers*. 2011;83(2):920-925
- [61] Kaur P, Thakur R, Barnela M, Chopra M, Manuja A, Chaudhury A. Synthesis, characterization and *in vitro* evaluation of cytotoxicity and antimicrobial activity of chitosan-metal nanocomposites. *Journal of Chemical Technology and Biotechnology* [Internet]. 2015;90(5):867-873. Available from: <http://doi.wiley.com/10.1002/jctb.4383> [accessed: January 31, 2017]
- [62] Ribič H, Kramar Z. Preprečevanje okužb, povezanih z zdravstvom: skripta za študijski program Zdravstvena nega (VS). Jesenice, Slovenia: Fakulteta za zdravstvo Jesenice; 2016. 115 p.
- [63] Kotnik Kevorkijan B. Enostavno širjenje bolezní. In: Južnič Sotlar M, editor. *Bolnišnične okužbe: klostridijska driska*. Ljubljana, Slovenia: Studio Moderna storitve d.o.o.; 2013. pp. 10-13

- [64] Wilks SA, Michels H, Keevil CW. The survival of *Escherichia coli* O157 on a range of metal surfaces. *The International Journal of Food Microbiology* [Internet]. 2005;**105**(3):445-454. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/16253366> [accessed: December 19, 2016]
- [65] Verran J, Redfern J, Smith LA, Whitehead KA. A critical evaluation of sampling methods used for assessing microorganisms on surfaces. *Food and Bioprocess Processing* [Internet]. 2010;**88**(4):335-340. Available from: <http://linkinghub.elsevier.com/retrieve/pii/S0960308510001021> [accessed: December 19, 2016]
- [66] Gubina M, Ihan A. *Medicinska bakteriologija z imunologijo in mikologijo*. Ljubljana: Medicinski razgledi; 2002. 543 p.
- [67] Fijan S, Koren S, Cencič A, Šostar-Turk S. Antimicrobial disinfection effect of a laundering procedure for hospital textiles against various indicator bacteria and fungi using different substrates for simulating human excrements. *Diagnostic Microbiology and Infectious Disease* [Internet]. 2007;**57**(3):251-257. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/17046191> [accessed: December 19, 2016]
- [68] Neely AN. A survey of gram-negative bacteria survival on hospital fabrics and plastics. *The Journal of Burn Care & Rehabilitation* [Internet]. 2000;**21**(6):523-527. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/11194806> [accessed: October 7, 2016]
- [69] Borkow G, Gabbay J. Biocidal textiles can help fight nosocomial infections. *Medical Hypotheses* [Internet]. 2008;**70**(5):990-994. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/17959322> [accessed: October 7, 2016]
- [70] Brunton WAT. Infection and hospital laundry. *Lancet*. 1995;**345**(8964):1574-1575
- [71] Wilcox MH, Jones BL. Enterococci and hospital laundry. *Lancet* [Internet]. 1995; **345**(8949):594. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/7776811> [accessed: December 19, 2016]
- [72] Barrie D, Hoffman PN, Wilson JA, Kramer JM. Contamination of hospital linen by *Bacillus cereus*. *Epidemiology and Infection* [Internet]. 1994;**113**(2):297-306. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/7925667> [accessed: December 19, 2016]
- [73] Gonzaga AJ, Mortimer EA, Wolinsky E, Rammelkamp CH, Wolinsky E, Mortimer EA, et al. Transmission of Staphylococci by fomites. *The Journal of the American Medical Association* [Internet]. 1964;**189**(10):711-715. Available from: <http://jama.ama-assn.org/cgi/doi/10.1001/jama.1964.03070100005001> [accessed: December 19, 2016]
- [74] Kirby WMM, Corpron DO, Tanner DC, Finland M, Kenney M, Schneierson SS, et al. Urinary tract infections caused by antibiotic-resistant coliform bacilli. *The Journal of the American Medical Association* [Internet]. 1956;**162**(1):1. Available from: <http://jama.jamanetwork.com/article.aspx?doi=10.1001/jama.1956.02970180003001> [accessed: December 19, 2016]

- [75] European Centre for Disease Prevention and Control. Antimicrobial resistance surveillance in Europe 2010. Surveillance Report; 2012. p. 202
- [76] Agency USEP. National Pesticide Information Retrieval System (NPIRS) [Internet]. 1998. Available from: [https://cfpub.epa.gov/si/si\\_public\\_record\\_Report.cfm?dirEntryID=2893](https://cfpub.epa.gov/si/si_public_record_Report.cfm?dirEntryID=2893) [accessed: January 27, 2017]
- [77] BI. Biocide Information [Internet]. 2004. Available from: <http://www.biocide-information.com/> [accessed: February 13, 2017]
- [78] National Industrial Chemicals Notification and Assessment Scheme. Chemical in Sanitized T99-19. [Internet]. 2007. Available from: <https://www.nicnas.gov.au/> [accessed: February 13, 2017]
- [79] McMahon T, Morrow M, Isbell D, Lantz T, Campbell McFarland J, Shamim N, et al. Reregistration Eligibility Decision for Trimethoxysilyl Quaternary Ammonium Chloride Compounds. Washington: United States Environmental protection Agency; 2007. 1-94 p.
- [80] Wijnhoven S, Peijnenburg W, Herberts C, Hagens W, Oomen A, Heugens E. Nano-silver—A review of available data and knowledge gaps in human and environmental risk assessment. *Nanotoxicology*. 2009;3:109-138
- [81] Dhende V, Hardin I, Locklin J. Durable antimicrobial textiles: Types, finishes and applications. In: Annis P, editor. *Understanding and Improving the Durability of Textiles*. Oxford, Cambridge, Philadelphia: Woodhead Publishing Limited; 2012. pp. 145-173
- [82] Russel A. Biocide usage and antibiotic resistance: The relevance of laboratory findings to clinical and environmental situations. *Lancet Infectious Diseases*. 2003;3:794-803
- [83] Yazdankhah SP, Scheie AA, Høiby EA, Lunestad B-T, Heir E, Fotland TØ, et al. Triclosan and antimicrobial resistance in bacteria: An overview. *Microbial Drug Resistance* [Internet]. 2006;12(2):83-90. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/16922622> [accessed: January 27, 2017]

